



# Texan Shale Chemicals

11806 Wilcrest Drive, Suite 202, Houston, TX 77031  
Phone: 281-741-0226 Email: Mani@Texanstone.com



## FRESHWATER VISCOSIFYING FRICTION REDUCER DPAM

The Friction reduction capabilities of TEXAN FR DRY FRESH are illustrated in the Technical Data sheet of Texan Dry Fresh posted on our website.

The proppant transport ability of a Polymer depends on two major factors:

- 1) Viscosity, 2) Elasticity.


### TEST METHODOLOGY

Two tests were carried out to analyze the proppant transport characteristics of Texan Dry Fresh: 1) Viscosity vs Shear Rate using Grace M3600 rheometer 2) Elasticity and Storage Modulus using Anton Paar rheometer in Amplitude sweep and Frequency Sweep

**Dosage:** 16 lbs. of FR/1000 gallons of Fresh Water (0.192 % solution)

**BLENDING RATE:** 1) 2500 RPM, 5 MIN; 2) 3200 RPM, 5 MIN

### RESULTS AND DISCUSSION:

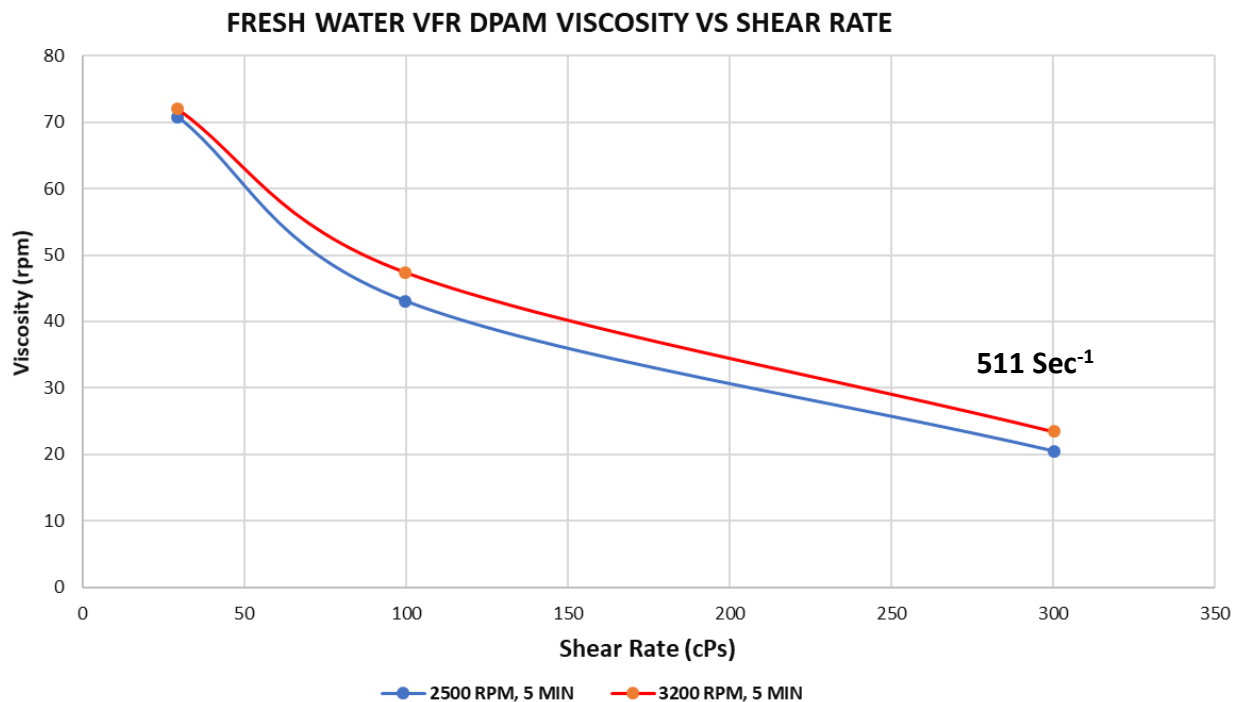

| Shear Rate (cPs) | Viscosity (rpm) |                 |
|------------------|-----------------|-----------------|
|                  | 2500 RPM, 5 MIN | 3200 RPM, 5 MIN |
| 29.37            | 70.8051         | 72.0052         |
| 99.87            | 43.0568         | 47.4095         |
| 300.18           | 20.509          | 23.4445         |

The viscosity readings at 300 rpm or 511 sec<sup>-1</sup> are above 20 cps in both blending parameters suggesting superior sand carrying ability with an increased dosage in Texan Dry Fresh.




# Texan Shale Chemicals

11806 Wilcrest Drive, Suite 202, Houston, TX 77031  
Phone: 281-741-0226 Email: Mani@Texanstone.com




## G' AND G'' ANALYSIS

Amplitude Sweep - Storage/Loss Modulus vs. Shear Strain  
6.28 rad/s Angular Frequency Constant ( $\omega$ ) | 75°F | Cone & Plate Geometry

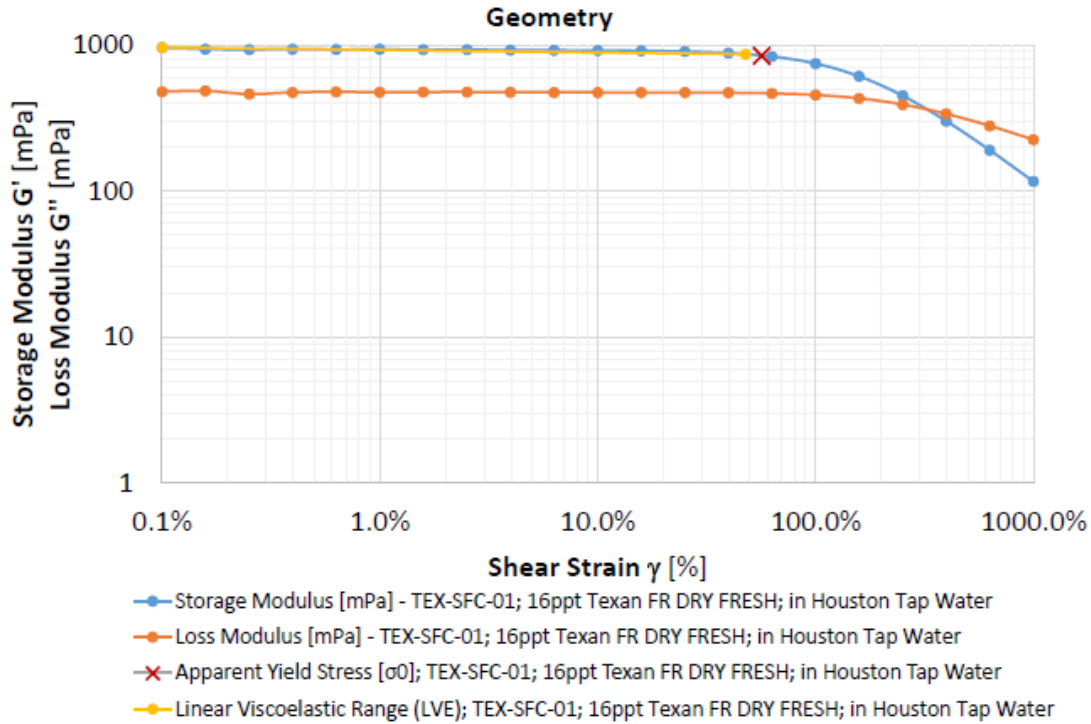

## Frequency Sweep - Storage/Loss Modulus vs. Angular Frequency

1.0 % Shear Strain (%) | 75°F | Cone & Plate Geometry

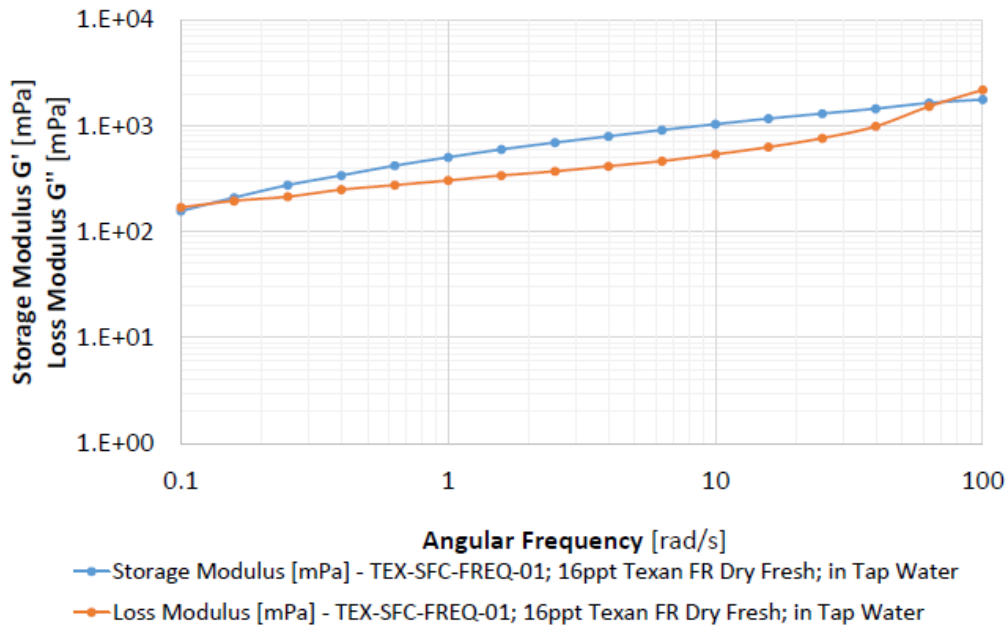

The amplitude and frequency sweep curves suggest that Texan Dry Fresh exhibits high elastic behavior or gel-like behavior over a wide range of Strain rate. Also, the high G' in the Linear Viscoelastic range suggests that the fluid exhibits strong viscoelastic behavior.